

Separation Between Antiferromagnetic and Ferromagnetic Transitions in $\text{Ru}_{1-x}\text{Cu}_x\text{Sr}_2\text{EuCu}_2\text{O}_{8+\delta}$

Y. Y. Xue¹, F. Chen¹, J. Cmaidalka¹, R. L. Meng¹, and C. W. Chu^{1,2,3}

¹*Department of Physics and Texas Center for Superconductivity,*

University of Houston, 202 Houston Science Center, Houston, Texas 77204-5002

²*Lawrence Berkeley National Laboratory, 1 Cyclotron Road, Berkeley, California 94720 and*

³*Hong Kong University of Science and Technology, Hong Kong*

(Dated: February 2, 2008)

The macroscopic magnetizations of $\text{Ru}_{1-x}\text{Cu}_x\text{Sr}_2\text{EuCu}_2\text{O}_{8+\delta}$ with x between 0 and 0.15 were investigated. A ferromagnet-like transition as well as an antiferromagnet-like transition appear around T_M in the low-field magnetization and around T_{AM} in the high-field differential susceptibility, respectively. The separation between them, which is accompanied by a flat plateau in the magnetic C_p , increases with x . Superparamagnetic $M(H)$ and slow spin dynamics, i.e. characteristics of nanomagnetic clusters, were observed far above T_M . A comparison with $\text{RuSr}_2(\text{Eu}_{1-y}\text{Ce}_y)\text{Cu}_2\text{O}_{10+\delta}$ and some manganites further suggests that a phase separation occurs, which can describe well the conflicting magnetic-superconductivity data previously reported.

PACS numbers: 74.81.-g, 74.72.-h, 75.40.Cx

The puzzling bulk, yet granular, superconductivity (SC) in rutheno-cuprates $\text{RuSr}_2\text{RCu}_2\text{O}_{8+\delta}$ (Ru1212R) and $\text{RuSr}_2(\text{R,Ce})_2\text{Cu}_2\text{O}_{10+\delta}$ (Ru1222R) with $\text{R} = \text{Gd, Eu, or Y}$,^{1,2,3,4} which coexists with a weak ferromagnetism (FM), is closely related to their magnetic structure. While a homogeneous canted antiferromagnetic (CAFM) spin-order may coexist with more-or-less ordinary superconductivity, such as the proposed Meissner state or the π -phase SC,^{2,5} magnetic inhomogeneity at length scales $\geq \xi$ will unavoidably lead to a Josephson-junction-array-like superconductivity,⁴ where ξ is the coherence length. In the case of Ru1222R, the reported data seem to indicate a rather complicated magnetic structure. Both the AFM-like differential-susceptibility maximum of the Ru ($\chi_{Ru \text{ only}}$) and the hyperfine splitting of the Mössbauer spectra, for example, occur at temperatures almost two times higher than the T_M , where an FM-like transition occurs in the low-field field-cooled magnetization (M_{FC}).^{1,6} Either a phase separation or a multistage transition, therefore, should occur.^{1,6} On the other hand, the situation of Ru1212R has been suggested to be different. The inflection point T_{AM} at $\partial^2(T\chi_{Ru \text{ only}})/\partial T^2 = 0$, which should be the Néel temperature in simple antiferromagnets,⁷ and the T_M are in rough agreement for a Ru1212Eu sample.⁸ Mean-field-like scaling has also been observed below T_M by both neutron powder diffraction (NPD) and zero-field nuclear magnetic resonance (ZFNMR).^{9,10} It is therefore natural that a simple CAFM was assumed in many previous investigations. This model, however, faces a dilemma in accommodating the magnetizations and the ZFNMR and NPD data. The NPD, for example, indicated that the Ru spins are AFM-aligned (G-type) along the c axis with a very tight upper limit of the FM components, i.e. < 0.1 and $\approx 0.2 \mu_B/\text{Ru}$ at $H = 0$ and $0.4 \text{ T} \leq H \leq 7 \text{ T}$, respectively.⁹ The spontaneous magnetization of the sample, however, reaches $M_r \approx 800 \text{ emu/mole}$, i.e. an FM component $0.28 \mu_B/\text{Ru}$ at $H = 0$. The extrapolated zero-field magnetization of $0.6 \mu_B/\text{Ru}$ at 50 K,⁸ which may serve as a lower limit for the FM component at 5 T, is again three times larger. The ZFNMR data, in addition, demonstrate that the Ru-spins should be aligned perpendicular to the c with a major (or dominant) FM component.¹⁰ This unusual magnetic structure, which appears as G-type AFM along c in NPD but ordered along a, b with a large FM component in both magnetization and NMR, suggested that the magnetic structure of Ru1212R deserved a reexamination. It should be pointed out that both the extremely broad C_p peak and the superparamagnet-like $M(H)$ up to $2 T_M$ in Ru1212Gd already suggest that its magnetic transition is far from simple:^{3,8} the spin correlations may exist up to $2 T_M$ with a significant entropy and a correlation size as large as $10^2\text{--}10^3 \mu_B$,⁶ both being characteristic of phase separation. It is interesting to note that both T_M and T_{AM} of Ru1212R can be tuned by Cu-doping.¹¹ The evolutions of M , $\chi_{Ru \text{ only}}$, and C_p of $\text{Ru}_{1-x}\text{Cu}_x\text{Sr}_2\text{EuCu}_2\text{O}_{8+\delta}$ with $0 \leq x \leq 0.15$, therefore, were measured. The T_M drops more than 25 K with x while the variation in T_{AM} is negligibly small. A separation between T_M and T_{AM} is developed with x . This separation is further accompanied by a magnetic C_p/T with a flat plateau between T_M and T_{AM} . Hence, a mesoscopic phase-separation is suggested.

Ceramic $\text{Ru}_{1-x}\text{Cu}_x\text{Sr}_2\text{EuCu}_2\text{O}_{8+\delta}$ samples with x between 0 and 0.15 were synthesized following the standard solid-state-reaction procedure. Precursors were first prepared by calcinating commercial oxides at 600–900 °C under flowing O_2 at 1 atm. Mixed powder with a proper cation-ratio was then pressed into pellets and sintered at 960 °C. The final heat treatment was done at 1065–1070 °C for 7 d in oxygen after repeatedly sintering and regrinding.⁴ The structure of the samples was determined by powder X-ray diffraction (XRD) using a Rigaku DMAX-IIIIB diffractometer. The x dependence of the lattice parameters, i.e. the $c \approx 11.553(2)$ to $11.550(2)$ Å for $x = 0$ and 0.15, respectively, is slightly weaker than that reported for $\text{Ru}_{1-x}\text{Cu}_x\text{Sr}_2\text{GdCu}_2\text{O}_{8+\delta}$.¹¹ Minor impurity phases, likely SrRuO_3 or oxides of (Sr,Cu),

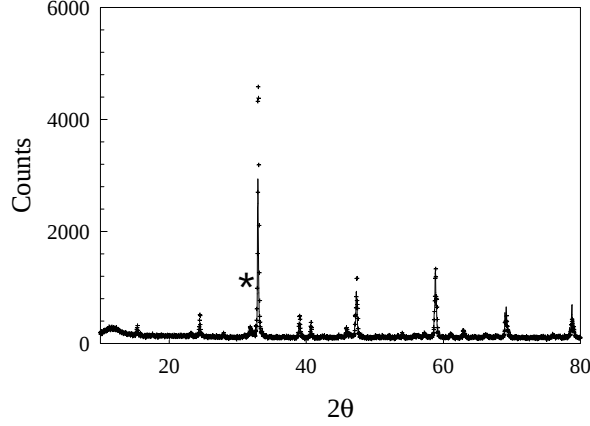


FIG. 1: The XRD of a $(\text{Ru}_{0.9}\text{Cu}_{0.1})\text{Sr}_2\text{EuCu}_2\text{O}_{8+\delta}$ sample. +: data; solid line: the Rietveld fit; *: the impurity lines.

are below 5% at $x \leq 0.15$ (Fig. 1). The composition was measured by a JEOL JXA 8600 electron microprobe with attached wavelength dispersive spectrometers (WDS). The local inhomogeneity of $1 - x$ is within the experimental resolution of ± 0.05 .¹² The magnetizations were measured using a Quantum Design SQUID magnetometer with an *ac* attachment and the specific heat was measured in a Quantum Design PPMS with a specific-heat attachment.

Superconductivity appears in all the samples below a critical temperature $T_c \approx 20\text{--}30$ K. A single-step jump of M_{FC} also appears with cooling at a higher temperature (Fig. 2a). According to the scaling correlation $(HM_0/MH_0)^{1/\gamma} = t + (M/M_0)^{1/\beta}$, the $\partial M/\partial T$ of an ideal ferromagnet should decrease with $t = (T - T_M)/T_M$ as $1/t^{\gamma+1}$ above T_M , but increase as $(-t)^{1-\beta}$ below, where $0 < \beta < 1$, $\gamma > 0$, H_0 , and M_0 are two critical exponents and two critical amplitudes, respectively. The situation for a CAFM magnet should be similar. Therefore, the inflection point of $M_{FC}(T)$ at 5 Oe, i.e. the temperature at which $\partial M_{FC}/\partial T$ peaks, is used as the T_M (Fig. 2a). The well defined T_M and the large FM component below T_M are in rough agreement with those reported for $\text{Ru}_{1-x}\text{Cu}_x\text{Sr}_2\text{GdCu}_2\text{O}_{8+\delta}$,⁸ but rather different from those of $\text{Ru}_{1-x}\text{Cu}_x\text{Sr}_2\text{GdCu}_2\text{O}_{8+\delta}$,¹¹ where no clear FM transition can be identified with $x \geq 0.1$. Differences in both the rare-earth elements and the synthesis procedures may contribute to the variation. It should be pointed out that the well defined T_M and the large M_{FC} of our samples make the analysis of M_{FC} and C_p easier and without significant interference from the minor impurities. A systematic decrease of T_M with x is observed, e.g. $T_M \approx 134$ K and 117 K at $x = 0$ and 0.1, respectively (Fig. 2a). It is also interesting to note that the reported bifurcation point between M_{ZFC} and M_{FC} , which should be very close to T_M if the domain pinning is strong, in $\text{Ru}_{1-x}\text{Cu}_x\text{Sr}_2\text{GdCu}_2\text{O}_{8+\delta}$ shows almost the same x dependence, i.e. down to ≈ 115 K and 100 K with $x = 0.1$ and 0.2, respectively.¹¹

The $\chi = M/H$ of a simple AFM magnet, which will be H -independent far above its AFM transition, should have a maximum slightly above the Néel temperature, T_{AM} . It has been suggested, in fact, that the magnetic energy,

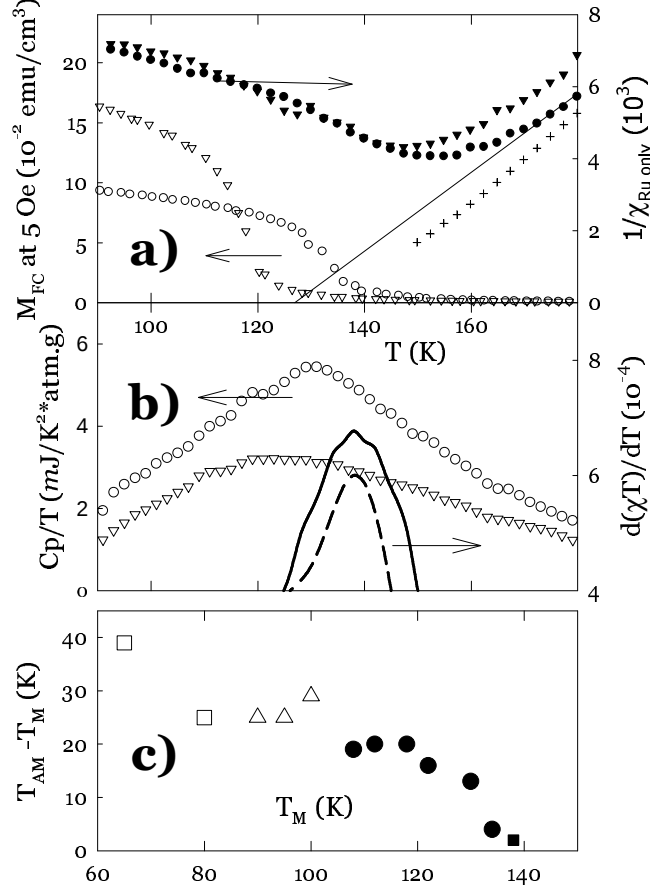


FIG. 2: a) The magnetizations. For the $x = 0$ sample, $\circ$: $M_{FC}(5 \text{ Oe})$; $+$: $H/M_{FC}(1 \text{ T})$; $\bullet$: $1/\chi_{Ru \text{ only}}$; solid line: C-W fit. For the $x = 0.1$ sample, ∇ : $M_{FC}(5 \text{ Oe})$; $\blacktriangledown$: $1/\chi_{Ru \text{ only}}$. b) The spin entropy. $\circ$: the magnetic C_p/T of the $x = 0$ sample; ∇ : that of the $x = 0.1$ sample; solid line: $\partial(T\chi)/\partial T$ of the $x = 0$ sample; dashed line: that of the $x = 0.1$ sample. c) The evolution of $T_{AM} - T_M$ with T_M . $\bullet$: Cu-doped Ru1212Eu; $\blacksquare$: Ru1212Eu of Butera *et al.*; $\triangle$: annealed Ru1222Gd; $\square$: as-synthesized Ru1222Eu.

E_m , and χ should both depend on the pair correlation functions $\Gamma(r) = 3[S^z(0)S^z(r)]/S(S+1)$ as $E_m \propto \Gamma_1$ and $\chi \propto [1 + \Sigma_r \Gamma(r)]/T \approx [1 + f(T)\Gamma_1]/T$, where $\Gamma(r)$, Γ_1 , and $f(T)$ are the pair-correlation with the pair distance $= r$, the correlation with the nearest-neighbor, and a slowly varying function of T , respectively.⁷ This leads to an approximation of $C_p \propto \partial(T\chi)/\partial T$ if the short-range correlation Γ_1 is dominant. T_{AM} , therefore, can be defined as the temperature of the $\partial(T\chi)/\partial T$ peak,⁷ which is observed close to the χ -maximum temperature in 3D but much lower in 2D.¹³ For CAFM magnets, an FM-like M_{FC} step may coexist with a $\partial(T\chi)/\partial T$ peak. However, $T_{AM} \approx T_M$ is expected, except for the possible H -induced transition shifts.¹⁴

To analyze the magnetization of $\text{Ru}_{1-x}\text{Cu}_x\text{Sr}_2\text{EuCu}_2\text{O}_{8+\delta}$, the Eu/CuO₂ contributions were first eliminated using the procedure previously proposed,⁸ i.e. with a Van Vleck susceptibility of free Eu^{3+} and a T -independent χ_0 of 8.7×10^{-4} emu/mole for CuO₂. For the undoped sample with $x = 0$, the Ru contribution is H -independent and follows a Curie-Weiss (C-W) fit only above 250 K with a C-W constant $\approx 2.6 \mu_B/\text{Ru}$ and a Curie temperature of 127 K. Deviation from the C-W fit and large superparamagnetic $M(H)$, however, develop at lower temperatures (Fig. 2a). The Ru contribution to χ at 1 T, for example, is more than 10% higher than that expected between 180 K and T_{AM} (Fig. 2a), indicating a dominant FM interaction. The 5 T differential Ru-susceptibility after subtracting the Eu/CuO₂ contributions ($\chi_{Ru \text{ only}}$), however, shows an opposite downturn, suggesting significant AFM interactions (Fig. 2a). In particular, a minimum of $1/\chi_{Ru \text{ only}}$ and a $\partial(T\chi)/\partial T$ peak appear around 157 K (Fig. 2a) and $T_{AM} \approx 138$ K (Fig. 2b), respectively, for the $x = 0$ sample. Undoped Ru1212Eu, therefore, might be interpreted as a simple CAFM

by either ignoring the 4 K difference between T_M and T_{AM} ,⁸ or by regarding it as a small H -induced transition shift.

To further confirm the presumed T_{AM} , the magnetic specific heat was measured at a zero field using a nonsuperconducting $\text{YBa}_2(\text{Cu}_{2.73}\text{Zn}_{0.27})\text{O}_7$ (YBCO) ceramic as the reference (Fig. 2b). The raw specific heat of Ru1212 is well above that of YBCO between 80 and 180 K, but the two merge outside this region, a situation similar to the data of Ru1212Gd.³ The magnetic C_p/T , i.e. the difference between Ru1212R and YBCO, shows a well defined peak at 133 K, which is only slightly lower than the 138 K $\partial(T\chi)/\partial T$ peak observed. This agreement between the C_p/T peak at zero field and the $\partial(T\chi)/\partial T$ peak at 5 T again demonstrates that the procedure of Fisher⁷ works reasonably well and that the H -induced transition shift is small in our case. It is also interesting to note the high- T tail of C_p/T and the non-C-W magnetization up to 180 K or higher (Figs. 2a,b). Significant short-range spin orders, therefore, should occur far above T_M and T_{AM} .

With the Cu doping, however, the T_M and the T_{AM} evolve in different ways and the separation between them broadens. At $x = 0.1$, for example, the T_M is quickly suppressed to 117 K but the $\partial(T\chi)/\partial T$ peak remains at 138 K (Figs. 2a,b). The accompanying C_p/T appears to broaden with x as well (Fig. 2b). In particular, the well defined peak evolves into a flat plateau between T_M and T_{AM} (Fig. 2b). It should also be pointed out that the separation at $x = 0.1$ is larger than the transition width in M_{FC} . Neither the sample inhomogeneity nor the experimental resolution, therefore, can account for the separation (Figs. 2a,b). The AFM-like $\partial(T\chi)/\partial T$ peak and the FM-like M_{FC} jump seem to carry distinct spin entropies of comparable strength.

It is therefore interesting to compare the data with that of Ru1222R, where two separate transitions have been observed in both magnetizations and Mössbauer spectra.^{1,6} The T_M and T_{AM} of $\text{Ru}_{1-x}\text{Cu}_x\text{Sr}_2\text{EuCu}_2\text{O}_{8+\delta}$ samples with $0 \leq x \leq 0.15$, the O_2/Ar -annealed $\text{RuSr}_2(\text{Gd}_{1.4}\text{Ce}_{0.6})\text{Cu}_2\text{O}_{10+\delta}$, and two as-synthesized Ru1222Eu samples are shown in Fig. 2c.⁶ The separation $T_{AM} - T_M$ increases systematically with decreasing T_M in the Cu-doped Ru1212Eu: from an extrapolated zero-separation at $T_M \approx 140$ K to 25 K at $T_M \approx 110$ K, where the data smoothly evolve into that of Ru1222R (Fig. 2c). The observation of $T_{AM} = T_M$ in the Ru1212Eu sample,⁸ therefore, may be only a coincidence. Distinct AFM and FM transitions may coexist in both Ru1212R and Ru1222R.

These two transitions, as has been argued in the case of Ru1222R,^{1,6} may be due to either a mesoscopic phase-separation or a multistage transition. The magnetic properties between T_M and T_{AM} , however, will be different in these two scenarios: some parts of Ru1212R should be in superparamagnetic states during phase separation, but should stay in a long-range spin-order state during a multistage transition. Evidence for the possible phase-separation in Ru1222R, for example, is found in both the superparamagnetic $M(H)$ with a magnetic cluster-size of $10^3 \mu_B$ and the slow spin dynamics far above T_{FM} .⁶ Similar properties were therefore tested in the Cu-doped Ru1212Eu.

The Langevin function with an additional linear term, $a \cdot H + m \cdot [c \tanh(\mu H/k_B T) - k_B T/\mu H]$, was used to fit the average magnetization in a M - H loop (inset, Fig. 3a).⁶ The fit is reasonably good with the deduced μ between 100 and $700 \mu_B/\text{cluster}$ (closed symbols in Fig. 3a), which is 4–5 times smaller than those deduced in Ru1222R, but still far larger than that expected based on the spin-fluctuations. A cluster of $400 \mu_B \approx 200$ Ru ions, for example, would be 4–5 nm or larger in an RuO layer. It should be further noted that the μ so-deduced may be only a lower limit of the actual cluster/spin-correlation length.¹⁵ The existence of such large clusters at $T/T_M > 1.1$ will be difficult to be interpreted as a simple fluctuation. This deduced size, on the other hand, appears to be too small for a crystalline magnet, as is suggested in the multistage transition model.

The dynamic spin-response was also studied. The logarithmic increase of M_{ZFC} at 5 Oe with time is almost unobservable, with the deduced rate of $d \ln M / d \ln t < 10^{-3}$ well within our experimental resolution, where $60 \text{ s} < t < 3600 \text{ s}$ is the time after the field switch. This is rather different from that of Ru1222Eu,⁶ but in agreement with the unobservable relaxation of Ru1212R ac -susceptibility reported between 1 s and 100 s.¹⁶ The lack of relaxations under the above conditions is apparently related to the cluster size in Ru1212R (Fig. 3a), which is 4–5 times smaller and leads to a quicker equilibrium. The slow spin dynamics, therefore, should either be explored in a shorter time window or after an enhancement of the energy barriers. Several different experimental conditions were then tested, and significant nonlogarithmic relaxations were observed in the remnant magnetization after a 50 Oe field-cooling (Fig. 3b). It is interesting to note that the energy barriers are $\approx KV_c - \mu H$ and KV_c , respectively, for the M_{ZFC} and the remnant magnetization, where K and V_c are the magnetic anisotropy and the coherent volume, respectively. This may make the remnant magnetization a more favorable candidate for investigating the slow dynamics. The strong T dependence of the relaxation observed (Fig. 3b) suggests, in our opinion, that the relaxation observed is unlikely an artifact of the SQUID magnetometer, but supports the existence of superparamagnetic clusters.

As pointed out earlier, the phase-separation model may also offer a consistent interpretation for the conflicting NPD/NMR and superconductivity data reported previously.⁶ The conflict between the NPD and NMR data for the magnetic structure, for example, may be attributed to the fact that the two probes have different sensitivities to various magnetic species, like those well documented in manganites.¹⁷ Similarly, the spatial separation between AFM and FM species offers a natural mechanism for the unusual superconductivity observed.⁴ Superconductivity can coexist with the AFM matrix. The finely dispersed FM clusters, on the other hand, depress the local SC order parameter and serve as tunnel barriers for the Cooper pairs. The superconductivity, therefore, may retain a significant part of

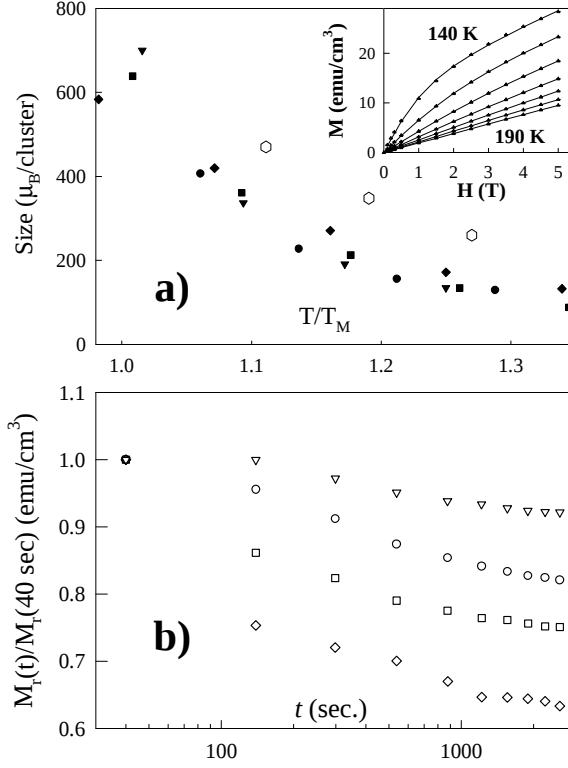


FIG. 3: a) The cluster sizes for samples with $\bullet$: $x = 0$; $\blacktriangledown$: $x = 0.05$; $\blacksquare$: $x=0.10$; and $\blacklozenge$: $x=0.15$ and for $\circ$: as-synthesized $\text{Ru}_{1222}\text{Eu}$ ($\times 4$). Inset: The isothermal $M(H)$ of the $x = 0$ sample. b) The relaxation of the remnant magnetizations at 160, 150, 140, and 130 K (from top to bottom) after field-cooling at 50 Oe.

the condensation energy, but appears only as a Josephson-junction array. Similarly, the critical temperature observed in the transport will naturally be much lower than that associated with the corresponding C_p anomaly,^{2,3} and can be easily suppressed by external fields.¹² The intragrain penetration depth will also be much longer than those expected based on the proposed universal $1/\lambda_2(T_c)$.⁴

In summary, a systematic separation between T_M and T_{AM} is observed in $\text{Ru}_{1212}\text{Eu}$ with Cu-doping, suggesting the coexistence of FM and AFM orders and the occurrence of a mesoscopic phase-separation in the compound. The superparamagnetic $M(H)$ as well as the slow spin-dynamics further support the interpretation.

Acknowledgments

The work in Houston is supported in part by NSF Grant No. DMR-9804325, the T. L. L. Temple Foundation, the John J. and Rebecca Moores Endowment, and the State of Texas through the Texas Center for Superconductivity at the University of Houston; and at Lawrence Berkeley Laboratory by the Director, Office of Science, Office of Basic Energy Sciences, Division of Materials Sciences and Engineering of the U.S. Department of Energy under Contract

No. DE-AC03-76SF00098.

-
- ¹ I. Felner, U. Asaf, Y. Levi and O. Millo, Phys. Rev. B **55**, 3374 (1997); I. Felner, U. Asaf and E. Galstyan, cond-mat/0111217 (2001).
 - ² C. Bernhard, J. L. Tallon, E. Brücher and R. K. Kremer, Phys. Rev. B **61**, 14960 (2000).
 - ³ J. L. Tallon, J. W. Loram, G. V. M. Williams and C. Bernhard, Phys. Rev. B **61**, 6471 (2000).
 - ⁴ Y. Y. Xue, B. Lorenz, R. L. Meng, A. Baikalov and C. W. Chu, Physica C **364-365**, 251 (2001); Y. Y. Xue, B. Lorenz, A. Baikalov, D. H. Cao, Z. G. Li and C. W. Chu, Phys. Rev. B **66**, 014503 (2002).
 - ⁵ W. E. Pickett, R. Weht and A. B. Shick, Phys. Rev. Lett. **83**, 3713 (1999).
 - ⁶ Y. Y. Xue, D. H. Cao, B. Lorenz and C. W. Chu, Phys. Rev. B **65**, 020511 (2001); Y. Y. Xue, B. Lorenz, D. H. Cao and C. W. Chu, cond-mat/0211342 (2002).
 - ⁷ M. E. Fisher, Philos. Mag. **7**, 1731 (1962).
 - ⁸ A. Butera, A. Fainstein, E. Winkler and J. Tallon, Phys. Rev. B **63**, 054442 (2001).
 - ⁹ J. W. Lynn, B. Keimer, C. Ulrich, C. Bernhard and J. L. Tallon, Phys. Rev. B **61**, 14964 (2000).
 - ¹⁰ Y. Tokunaga, H. Kotegawa, K. Ishida, Y. Kitaoka, H. Takagiwa and J. Akimitsu, Phys. Rev. Lett. **86**, 5767 (2001).
 - ¹¹ P. W. Klamut, B. Dabrowski, S. Kolesnik, M. Maxwell and J. Mais, Phys. Rev. B **63**, 224512 (2001).
 - ¹² B. Lorenz, Y. Y. Xue, R. L. Meng and C. W. Chu, Phys. Rev. B **65**, 174503 (2002).
 - ¹³ L. J. de Jongh and A. R. Miedema, Adv. Phys. **23**, 1 (1974).
 - ¹⁴ This is true below a critical field H_c since $\partial(T\chi)/\partial T$ and $\partial M_{FC}/\partial T$ have similar T -dependences. Above H_c , however, the field may break the AFM spin-correlations and a magnetization jump appears. A. Herweijer *et al.* reported in Phys. Rev. B **5**, 4618 (1972), for example, that the magnetizations of $\text{CsCoCl}_3 \cdot 2\text{H}_2\text{O}$ (a 1D CAFM) are linear in H below 0.3 T with identical T_{AM} and T_M .
 - ¹⁵ P. Allia, M. Coisson, P. Tiberto, F. Vinai, M. Knobel, M. A. Novak and W. C. Nunes, Phys. Rev. B **64**, 144420 (2001), and references therein.
 - ¹⁶ I. Živković, Y. Hirai, B. H. Frazer, M. Prester, D. Drobac, D. Ariosa, H. Berger, D. Pavuna, G. Margaritondo, I. Felner and M. Onellion, Phys. Rev. B **65**, 144420 (2002).
 - ¹⁷ Cz. Kapusta, P. C. Riedi, M. Sikora and M. R. Ibarra, Phys. Rev. Lett. **84**, 4216 (2000).